arXiv:1204.2958v3 [cond-mat.mtrl-sci] 19 Apr 2012

Can we trust the temperature - misfit strain thin film phase diagrams?

Alexander Kvasov and Alexander K. Tagantsev
Ceramics Laboratory
École Polytechnique Fédérale de Lausanne
CH-1015 Lausanne, Switzerland

(Dated: March 2, 2013)

It was demonstrated that phenomenological approach based on Landau thermodynamic theory widely used for modeling of ferroelectrics can lead to a substantial inaccuracy of description of thermodynamics of ferroelectric thin films if non-linear electrostriction and non-linear elastic compliance are not taken into account. In this paper we demonstrate this with an example of the temperature - misfit strain phase diagrams of a single-domain (001)-oriented $BaTiO_3$ thin film. Non-linear electrostriction and non-linear compliance tensors were calculated using first principles methods.

PACS numbers: 77.80.Dj, 77.84.-s, 81.30.-t

Strain engineering is a modern strategy to control and enhance material properties. It represents a technique which deals with semiconductor and ferroelectric thin films strained on a substrate. Such strain can be tensile or compressive and occurs due to a difference between lattice parameters of the film and that of the underlying substrate. In strain engineering, a strain appeared in the film shifts the paraelectric-to-ferroelectric transition temperature and thus can change the properties of the material such as dielectric and piezoelectric constants, remanent polarization, or even can induce the ferroelectricity in a non-ferroelectric material [1]. To describe the ferroelectric state of a strained film, it was found to be very convenient to use temperature - misfit strain phase diagrams. First introduced by Pertsev et al. [2] such diagrams present polarization state depending on temperature and strain appeared in the film after deposition it on the substrate. They have been developed for many classical ferroelectric materials such as $BaTiO_3$[2–6], $PbTiO_3$[3, 4], and $SrTiO_3$[7], etc.

Theoretical study of temperature - misfit strain phase diagrams can provide strain engineering and relevant experiments with guide lines. For example, the first phase diagrams developed by Pertsev et al. [2, 3] shortly stimulated experiments which confirmed the theoretical predictions, demonstrating huge misfit strain effects on ferroelectric properties of $BaTiO_3$ [8].

Calculations of such diagrams involve Landau theory or *ab initio* microscopic approach. The first principles calculations [6] are more and more potent nowadays but require a lot of computations and there still exists a variety of problems where phenomenological approach can be valuable. Phenomenological approach is based on Landau-Ginzburg-Devonshire thermodynamic theory which is widely used for phase field modeling [5], for calculations of single-domain [3] and poly-domain [4] thin film diagrams. However, there is a considerable difference between the results obtained by first-principle calculations and by calculations based on Landau phenomenological theory [3, 6]. What is the reason of such disparity? There is no doubt that to have reliable description of a strained system based on thermodynamic theory one has to know precisely the coefficients of thermodynamic energy expansion which are not always easy to get experimentally. However, if we suppose that we know these coefficients enough precise, can then the thermodynamic description of a strained system be trusted? This question was already raised [9] in the context of $PbTiO_3$ thin film of (111)-orientation and it was suggested that a classical set of thermodynamic coefficients not including non-linear electrostriction can be insufficient for reliable description of a strained ferroelectric film. The goal of this paper is to clarify this issue to show that non-linear electrostriction and non-linear mechanical compliance can substantially affect the thermodynamics of thin ferroelectric films.

The problem with the standard description of strained ferroelectrics can be illustrated qualitatively by a simple scalar model. Let us describe a ferroelectic with a Gibbs thermodynamic potential energy expansion keeping only one component of polarization P and stress σ:

$$G = \underbrace{\frac{\alpha}{2}P^2 + \frac{\beta}{4}P^4 + \frac{\gamma}{6}P^6 - \frac{s}{2}\sigma^2 - QP^2\sigma}_{\text{"ordinary"}} - \underbrace{\frac{M}{2}P^2\sigma^2 - RP^4\sigma - \frac{N}{3}\sigma^3}_{\text{"high-order"}}, \tag{1}$$

where "ordinary" part represents Gibbs energy commonly used to describe ferroelectric systems and "high-order" terms (M, R - high-order electrostrictive coefficients and N - non-linear compliance) which are customarily neglected. This neglect can be readily justified for a bulk material but the situation for a clamped system is different. We can show this considering ferroelectricity in a clamped system, i.e. where the strain ϵ equals the misfit strain ϵ_0. To obtain an effective potential $\widetilde{G}(T, P, \epsilon_0) = G + \epsilon\sigma$, T - temperature, for the clamped system, we eliminate stress σ using mechanical equation of state

$$\epsilon = -\frac{\partial G}{\partial \sigma} = s\sigma + N\sigma^2 + QP^2 + RP^4 + MP^2\sigma, \tag{2}$$

and write the $\widetilde{G}(T, P, \epsilon_0)$:

$$\widetilde{G} = \frac{\alpha^*}{2}P^2 + \frac{\beta^*}{4}P^4 + \frac{\gamma^*}{6}P^6 + \frac{\epsilon_0^2}{2s}. \tag{3}$$

Electro-mechanical interactions in such system lead to renormalizations of α, β and γ:

$$\alpha^* = \alpha - \epsilon_0\frac{Q}{s} - \underbrace{\epsilon_0^2\left(\frac{M}{2s^2} + \frac{QN}{s^3}\right)}_{\text{A}}, \tag{4}$$

$$\beta^* = \beta + 2\frac{Q^2}{s} + \underbrace{\epsilon_0(\frac{MQ}{s^2} - \frac{R}{s} - \frac{NQ^2}{s^3})}_{\text{B}}, \tag{5}$$

$$\gamma^* = \gamma - \underbrace{3M\frac{Q^2}{s^2} + 6R\frac{Q}{s} + 2N\frac{Q^3}{s^3}}_{\text{C}}. \tag{6}$$

Atomic order-of-magnitude estimates show that the corrections due to high-order coefficients A and B are expected to be small as compared to corrections $\epsilon_0\frac{Q}{s}$ for α and $2\frac{Q^2}{s}$ for β (except the cases where the low-order corrections are unusually small) whereas C correction may be of the same order of magnitude as γ (6). This situation is similar the strong renormalization of β term (charge of sign) in BaTiO$_3$ films caused by electrostriction [3]. These estimates suggest that the high-order coefficients, which are customarily neglected in majority of problems, should be included into thermodynamic energy expansion as far as γ is important for the description of a problem.

To illustrate this phenomenon quantitatively, we demonstrate the influence of high-order terms on the temperature - misfit strain phase diagram for a single-domain (001)-oriented BaTiO$_3$ thin film. To plot the diagram, we use Landau-Ginsburg-Devonshire thermodynamic theory with boundary conditions applied to a 2D clamped film on the substrate. We start with the Gibbs expansion with respect to polarization P_i and stress σ_i (Hereafter we use the Voigt matrix notation and assume summation over repeated indices.):

$$G = a_i P_i^2 + a_{ij}P_i^2P_j^2 + a_{ijk}P_i^2P_j^2P_k^2 - \frac{s_{ij}}{2}\sigma_i\sigma_j - \frac{N_{ijk}}{3}\sigma_i\sigma_j\sigma_k - Q_{ij}P_i^2\sigma_j - \frac{M_{ijk}}{2}P_i^2\sigma_j\sigma_k - R_{ijk}P_i^2P_j^2\sigma_k, \tag{7}$$

where a_i, a_{ij}, and a_{ijk} are dielectric stiffness and higher-order stiffness coefficients at constant stress, s_{ij} and N_{ijk} are linear and nonlinear elastic compliances, Q_{ij} ordinary electrostriction, and M_{ijk} and R_{ijk} are high-order electrostriction tensors. To obtain effective potential $\widetilde{G}(P_i, T, \epsilon_0) = G + \epsilon_1\sigma_1 + \epsilon_2\sigma_2 + \epsilon_6\sigma_6$, the minima of which correspond to the ground state of the film, we apply mixed boundary conditions ($\frac{\partial G}{\partial\sigma_1} = \epsilon_0$, $\frac{\partial G}{\partial\sigma_2} = \epsilon_0$, $\frac{\partial G}{\partial\sigma_6} = 0$ and $\sigma_3 = 0, \sigma_4 = 0, \sigma_5 = 0$) [3] and eliminate σ_1, σ_2 and σ_6. Hereafter Cartesian coordinate system with the x_3 axis perpendicular to the film-substrate interface is considered, $\epsilon_0 = \frac{a_\parallel - a_0}{a_0}$ - biaxial parent misfit strain, where a_0 is the lattice parameter of the ferroelectric in the cubic phase extrapolated to temperature T and $a_\parallel$ is the in-plane lattice parameter of the film. The function $\widetilde{G}$ obtained depends on P_i, T, and ϵ_0. Minimizing $\widetilde{G} = \widetilde{G}(P_i, T, \epsilon_0)$ with respect to polarization P_i for each (T, ϵ_0) point one can build the whole phase diagram.

To see what impact high-order interactions exert on the strained BaTiO$_3$ thin film, we should know the values of high-order electrostrictive and non-linear compliance tensors themselves, which are not yet available experimentally. Consequently we turned towards *ab initio* methods, namely, we used Vienna Ab-initio Simulation Package (VASP) [10] performing zero Kelvin Density Functional Theory (DFT) full relaxation calculations. All calculations were performed within the generalized-gradient approximation as implemented in VASP using the projector augmented-wave method for the electron-ion interactions [11]. We have used a 6x6x6 Monkhorst-Pack grid for k-point sampling [12], and a plane-wave energy cut-off of 600eV. For full relaxation calculations, the threshold of Hellman-Feynman force was less than 1meV/A. Here we would like to underline that mechanical and electro-mechanical properties, like mechanical compliance and electrostriction in (7), are expected to be weakly temperature dependent, what justifies the use of zero Kelvin DFT results in finite temperature calculations.

As the first step, using VASP we obtained all components of the 6th-rank high-order electrostrictive tensors m_{ijk} and r_{ijk} as well as of non-linear compliance n_{ijk} of Helmholtz thermodynamic function F written in terms of polarization P_i and strain ϵ_i:

$$F = b_i P_i^2 + b_{ij}P_i^2P_j^2 + b_{ijk}P_i^2P_j^2P_k^2 + \frac{c_{ij}}{2}\epsilon_i\epsilon_j + \frac{n_{ijk}}{3}\epsilon_i\epsilon_j\epsilon_k - q_{ij}P_i^2\epsilon_j - \frac{m_{ijk}}{2}P_i^2\epsilon_j\epsilon_k - r_{ijk}P_i^2P_j^2\epsilon_k. \tag{8}$$

Technically, because of working with DFT, it is more convenient for us to use F expansion than G. When the c_{ij}, n_{ijk}, q_{ij}, m_{ijk}, and r_{ijk} coefficients are known, one can find coefficients s_{ij}, N_{ijk}, Q_{ij}, M_{ijk}, and R_{ijk} for expansion G. The relations between coefficients of G and F, in view of their complexity, are presented in Supplemental Materials at [URL inserted by publisher].

Let us briefly demonstrate the way we found stiffness c_{ij} and n_{ijk} and electrostrictive q_{ij}, m_{ijk}, and r_{ijk} coefficients. Using VASP we find $\sigma(\epsilon)$ and $P(\epsilon)$ dependencies, then we put them to mechanical state equation

$$\sigma_h = c_{hj}\epsilon_j + n_{hjk}\epsilon_j\epsilon_k - q_{ih}P_i^2 - m_{ijh}P_i^2\epsilon_j - r_{ijh}P_i^2P_j^2, \tag{9}$$

and determine the coefficients by fitting. It is possible to find c_{ij} and n_{ijk} tensors separately from others (q_{ij}, m_{ijk}, and r_{ijk}) if one uses the mechanical state equation (9) at zero polarization and model deformation to paraelectric cubic phase with VASP (keeping mmm symmetry of the structure). Then the other coefficients can be found from analysis of the full Eq. (9). Further for simplicity we demonstrate how to find q_{11}, m_{111} and r_{111} tensors components. One uses Eq. (9) for the case where only polarization P_1 and strain ϵ_1 are nonzero:

$$\sigma_1 = c_{11}\epsilon_1 + n_{111}\epsilon_1^2 - q_{11}P_1^2 - m_{111}P_1^2\epsilon_1 - r_{111}P_1^4. \tag{10}$$

Using VASP full relaxation calculations and keeping $4mm$ tetragonal symmetry of the structure, we find $P_1(\epsilon_1)$ and $\sigma_1(\epsilon_1)$ dependences (polarization was calculated by atom displacements and Born charges which were calculated for the cubic phase) and substitute them into Eq. (10). Once we have polynomial functions of ϵ_1 on the both sides of Eq. (10) we can obtain q_{11}, m_{111}, and r_{111}. By repetition of such a procedure for different symmetries of the structure and for different components of σ_i and ϵ_j it is possible to calculate all the components of the high-order electrostrictive tensors.

The coefficients of ordinary and high-order electrostriction as well as linear and non-linear elastic compliances obtained with the first principles calculations are given in the Table I. Here, we should notice that current DFT methods give relatively moderate precision for high-order coefficients as it is clear from the error bars in Table I.

$s, [10^{-12}\frac{1}{\mathrm{Pa}}]$		$Q, [\frac{\mathrm{m}^4}{\mathrm{C}^2}]$		$M, [10^{-12}\frac{\mathrm{m}^4}{\mathrm{C}^2\mathrm{Pa}}]$		$R, [\frac{\mathrm{m}^8}{\mathrm{C}^4}]$		$N, [10^{-23}\frac{1}{\mathrm{Pa}^2}]$	
s_{11}	4.25 ± 0.01	Q_{11}	0.11 ± 0.01	M_{111}	-5.6 ± 0.6	R_{111}	0.5 ± 0.1	N_{111}	8 ± 1
s_{12}	-1.14 ± 0.01	Q_{12}	0.04 ± 0.01	M_{112}	0.8 ± 0.5	R_{121}	< 0.2	N_{112}	< 2
s_{44}	8.45 ± 0.01	Q_{44}	0.04 ± 0.01	M_{122}	1.6 ± 0.6	R_{112}	-0.8 ± 0.1	N_{123}	< 2
				M_{123}	< 0.5	R_{123}	-0.3 ± 0.2	N_{144}	< 2
Q from [3], $[\frac{\mathrm{m}^4}{\mathrm{C}^2}]$		$Q_{\mathrm{trad}}, [\frac{\mathrm{m}^4}{\mathrm{C}^2}]$		M_{144}	< 1.6	R_{144}	< 0.2	N_{155}	< 2
Q_{11}	0.11	Q_{11}	0.15	M_{155}	4.4 ± 1.4	R_{155}	< 0.2	N_{456}	< 4
Q_{12}	-0.043	Q_{12}	-0.03	M_{414}	< 1				
Q_{44}	0.059	Q_{44}	0.04	M_{424}	< 1				
				M_{456}	< 1				

TABLE I. Some material parameters of $\mathrm{BaTiO_3}$ obtained from *ab initio* calculations. s_{ij}, N_{ijk}, Q_{ij}, M_{ijk}, and R_{ijk} are elastic compliance, nonlinear elastic compliance, electrostrictive tensor, and high-order electrostrictive tensors, respectively.

As it was said above, discussing the scalar model, these high-order coefficients lead to changes of tensors of coefficients $a_{ijk} \rightarrow a^*_{ijk}$ of P^6-terms while passing from a bulk crystal to the thin film ($G \rightarrow \widetilde{G}$). Table II demonstrate the size of this effect for $\mathrm{BaTiO_3}$ (for detailed information on a^*_{ijk} renormalization see Supplemental Materials at [URL inserted by publisher]) where the components of the original and renormalized tensors as well as the renormolizing corrections are given. "Corrections" represent an addition to a_{ijk}, for example $a^*_{333} = a_{111} + \Delta a^*_{333}$.

Bulk	Correction	Film
$a_{111} = 8$	$\Delta a^*_{111} = 4$ $\Delta a^*_{333} = -20$	$a^*_{111} = 12 \pm 3$ $a^*_{333} = -12 \pm 3$
$a_{112} = 5$	$\Delta a^*_{112} = -31$ $\Delta a^*_{113} = -27$ $\Delta a^*_{133} = -51$	$a^*_{112} = -26 \pm 4$ $a^*_{113} = -22 \pm 5$ $a^*_{133} = -46 \pm 5$
$a_{123} = 5$	$\Delta a^*_{123} = -62$	$a^*_{123} = -57 \pm 20$

TABLE II. (Column 1) coefficients a_{ijk} of P^6-terms in $10^9\,\frac{\mathrm{m}^9}{\mathrm{C}^4\mathrm{F}}$ at 300K of expansion G for bulk and mechanically free $\mathrm{BaTiO_3}$; (Column 2) corrections for corresponding a^*_{ijk}; (Column 3) a^*_{ijk} of $\widetilde{G}$ of a (001) clamped film of $\mathrm{BaTiO_3}$.

Inspection of this table shows that the renormarization is strong, confirming the conclusion drawn above from the order-of-magnitude estimates. Another striking feature of the data from the table is negative sign of some of a^*_{ijk}, making the renormalized theory formally unstable. However, we found that physically the situation can be treated as stable. The point is that the potential $\widetilde{G}$ of thin film still has local minima due to the positive sign of renormalized coefficients for P^4-terms of $\widetilde{G}$ (as in Ref. [3]), therefore the system is locally stable. As for the global stability, it can be restored by adding P^8-terms G expansion [13]. We do not incorporate these terms in our consideration, however we believe that this will not essentially affect the positions of the local minima in view of very high power of the terms.

Figures 1(a) and 1(b) show how original phase diagram built with the coefficients from [3] changes when supplemented with the high-order coefficients from our first principles calculations. Taking into account the high-order

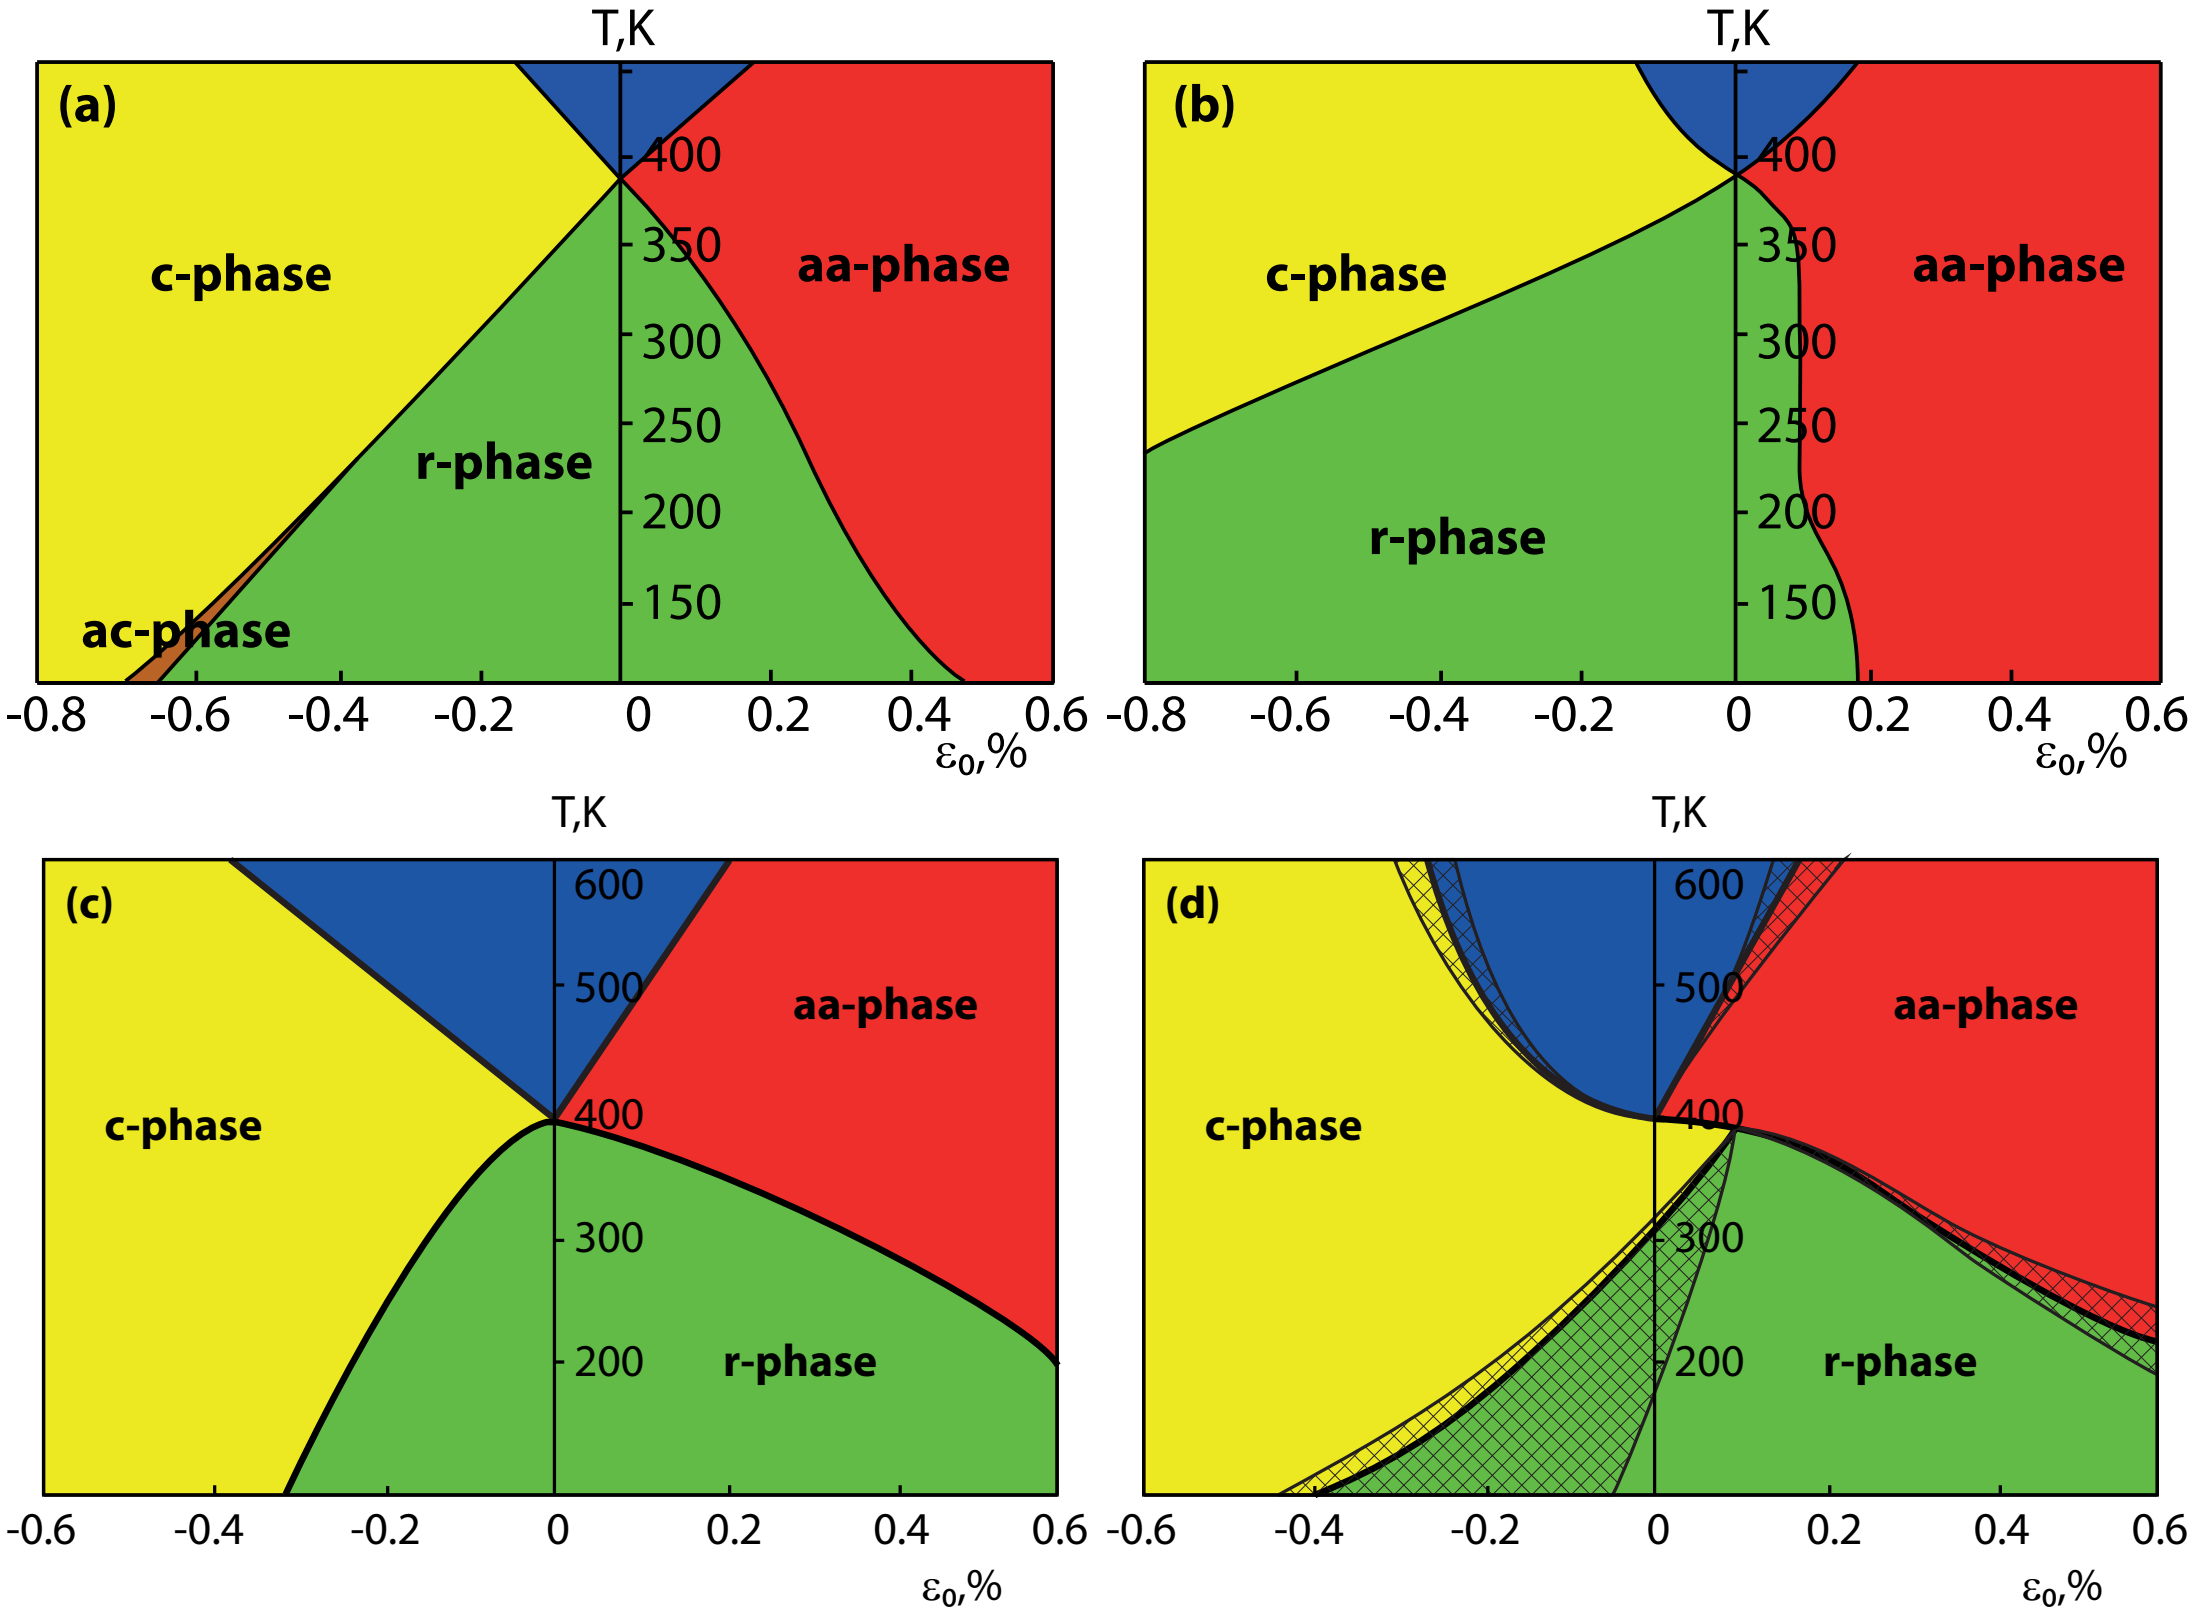

FIG. 1. Temperature - misfit strain phase diagrams of a single-domain (001)-oriented BaTiO$_3$. ϵ_0 - biaxial parent misfit strain, T - temperature. The phases are denoted as (i) the c-phase (yellow), polarization is out-of-plane ($P_1 = P_2 = 0, P_3 \neq 0$); (ii) the aa-phase (red), where polarization is in-plane ($P_1 \neq 0, P_2 \neq 0, P_3 = 0$); (iii) the ac-phase (brown) where $P_1 \neq 0, P_2 = 0, P_3 \neq 0$; (iv) r-phase (red), where all components of polarization are non-zero; and (v) paraelectric phrase (blue), polarization is 0. (a) Original Pertsev's diagrams built with coefficients from [3]. (b) Developed with coefficients set from [3] appended with high-order M_{ijklmn}, R_{ijklmn} and N_{ijklmn} coefficients. For (c) and (d) elastic and electromechanical couplings were obtained from first principles calculations. (c) Calculated with "traditional" electrostrictive coefficients used for description of all electromechanical couplings, *no high-order terms.* (d) Calculated with the full set of electromechanical coefficients. The hatched regions demonstrate the shift of the transition lines within the error bars of the coefficients.

coefficients strongly changes the diagram: phase transition lines become shifted and ac-phase is disappeared like in [6]. In the case of BaTiO$_3$ M_{ijk} and N_{ijk} do not give large contributions while R_{ijk} plays the major rule.

An interesting fact we would like to mention is the positive sign of Q_{12} electrostrictive coefficient we obtained. At the same time, if we follow the "traditional" way of calculating electrostriction coefficients as $Q_{12}^{\text{trad}} = \frac{\epsilon_{S1}}{P_{S2}^2}$, where P_S is a value of spontaneous polarization and ϵ_S is a value of spontaneous strain in tetragonal phase, our "traditional value" of Q_{12}^{trad} is negative and close to those previously reported [3, 14] (see Table I). The implication is that the high-order electrostrictive coefficient R_{112} was found anomalously large so that, when polarization and strain reach their spontaneous values, R_{112} strongly influences the "traditional" electrostriction which actually includes contributions of Q_{12} and R_{112}:

$$Q_{12}^{\text{trad}} = \frac{\epsilon_{S1}}{P_{S2}^2} = \frac{Q_{12}P_{S2}^2 + R_{112}P_{S2}^4}{P_{S2}^2} = Q_{12} + R_{112}P_{S2}^2. \tag{11}$$

We double checked the positive sign of Q_{12}, performing frozen phonon calculations to obtain a positive Q_{12} about $0.03\frac{m^4}{C^2}$.

In view that electrostrictive coefficients were found different from those used in [3] it's instructive to plot the phase diagram where all elastic and electro-mechanical coefficients are taken from *ab initio* calculations. Figures 1(c) and 1(d) show two diagrams based on *ab initio* calculations. Figure 1(c) is calculated within the standard framework (where all electromechanical effects are described with conventional electrostriction coefficients) using the "traditional" scheme for the treatment of our VASP data. Figure 1(d) is developed using the full set of coefficients including high-order terms obtained from the same data. The hatched regions demonstrate the shift of the transition lines within the error bars of the coefficients, in the hatched region between c-phase and r-phase a new ac-phase can appear similar to Fig. 1(a). It is seen that the diagram is extremely sensitive to the variation of the high-order coefficients which have relatively low precision as it can be seen from Table I.

Our analysis shows that an adequate Landau theory treatment of thermodynamics of ferroelectric thin films (single-domain and poly-domain thin films calculations, and phase field modeling) requires taking into account high-order electromechanical couplings and non-linear elasticity. In view of this finding, we believe that an experimental evaluation of high-order electromechanical couplings in ferroelectrics seems to be a tack of primarily importance.

[1] J. H. Haeni, P. Irvin, W. Chang, R. Uecker, P. Reiche, Y. L. Li, S. Choudhury, W. Tian, M. E. Hawley, B. Craigo, A. K. Tagantsev, X. Q. Pan, S. K. Streiffer, L. Q. Chen, S. W. Kirchoefer, J. Levy, and D. G. Schlom, Nature **430**, 758 (2004).

[2] N. A. Pertsev, A. G. Zembilgotov, and A. K. Tagantsev, Physical Review Letters **80**, 1988 (1998).

[3] N. A. Pertsev, Z. G. Zembilgotov, and A. K. Tagantsev, Ferroelectrics **223**, 79 (1999).

[4] V. G. Koukhar, N. A. Pertsev, and R. Waser, Phys. Rev. B **64**, 214103 (2001).

[5] Y. L. Li, S. Y. Hu, Z. K. Liu, and L. Q. Chen, Applied Physics Letters **78**, 3878 (2001).

[6] O. Diéguez, S. Tinte, A. Antons, C. Bungaro, J. B. Neaton, K. M. Rabe, and D. Vanderbilt, Phys. Rev. B **69**, 212101 (2004).

[7] N. A. Pertsev, A. K. Tagantsev, and N. Setter, Physical Review B **61**, R825 (2000).

[8] K. J. Choi, M. Biegalski, Y. L. Li, A. Sharan, J. Schubert, R. Uecker, P. Reiche, Y. B. Chen, X. Q. Pan, V. Gopalan, L. Q. Chen, D. G. Schlom, and C. B. Eom, Science **306**, 1005 (2004).

[9] A. K. Tagantsev, N. A. Pertsev, P. Muralt, and N. Setter, Phys. Rev. B **65**, 012104 (2001).

[10] G. Kresse and J. Furthmuller, Physical Review B **54**, 11169 (1996).

[11] G. Kresse and D. Joubert, Physical Review B **59**, 1758 (1999).

[12] H. J. Monkhorst and J. D. Pack, Physical Review B **13**, 5188 (1976).

[13] Y. L. Wang, A. K. Tagantsev, D. Damjanovic, N. Setter, V. K. Yarmarkin, A. I. Sokolov, and I. A. Lukyanchuk, Journal of Applied Physics **101**, 9 (2007).

[14] T. Yamada, Journal of Applied Physics **43**, 328 (1972).

SUPPLEMENTARY MATERIALS

Knowing the coefficients of Helmholtz thermodynamic function F written in terms of polarization P_i and strain ϵ_i

$$F = b_i P_i^2 + b_{ij} P_i^2 P_j^2 + b_{ijk} P_i^2 P_j^2 P_k^2 + \frac{c_{ij}}{2} \epsilon_i \epsilon_j + \frac{n_{ijk}}{3} \epsilon_i \epsilon_j \epsilon_k - q_{ij} P_i^2 \epsilon_j - \frac{m_{ijk}}{2} P_i^2 \epsilon_j \epsilon_k - r_{ijk} P_i^2 P_j^2 \epsilon_k. \qquad (12)$$

it is possible to find the corresponding coefficients of Gibbs energy expansion G with respect to polarization P_i and stress σ_i

$$G = a_i P_i^2 + a_{ij} P_i^2 P_j^2 + a_{ijk} P_i^2 P_j^2 P_k^2 - \frac{s_{ij}}{2} \sigma_i \sigma_j - \frac{N_{ijk}}{3} \sigma_i \sigma_j \sigma_k - Q_{ij} P_i^2 \sigma_j - \frac{M_{ijk}}{2} P_i^2 \sigma_j \sigma_k - R_{ijk} P_i^2 P_j^2 \sigma_k. \qquad (13)$$

One performs Legendre transformation

$$G = F - \sum_{i=1}^{6} \epsilon_i \sigma_i \qquad (14)$$

where $\sum \epsilon_i \sigma_i$ represents a work required to maintain a constant strain. Then using mechanical equation of state

$$\sigma_i = -\frac{\partial F}{\partial \epsilon_i}, i = 1..6 \qquad (15)$$

one eliminates stresses ϵ_i between (14) and (15): solutions of Eqs. (15) were expanded in series and only low order terms of the expansion were kept, then ϵ_i were substituted into (14).

The transformations of the corresponding high-order electrostrictive coefficients are listed below (16 - 30).

$$M_{111} = \frac{(c_{11}+c_{12})^2 m_{111}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{4c_{12}(c_{11}+c_{12}) m_{112}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} + \frac{2c_{12}^2 m_{122}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} + \frac{2c_{12}^2 m_{123}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2}, \qquad (16)$$

$$M_{112} = -\frac{c_{12}(c_{11}+c_{12}) m_{111}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} + \frac{\left(c_{11}^2 + c_{11}c_{12} + 2c_{12}^2\right) m_{112}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{c_{11}c_{12} m_{122}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{c_{11}c_{12} m_{123}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2}, \qquad (17)$$

$$M_{122} = \frac{c_{12}^2 m_{111}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{2c_{11}c_{12} m_{112}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} + \frac{\left(c_{11}^2 + 2c_{11}c_{12} + 2c_{12}^2\right) m_{122}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{2c_{12}(c_{11}+c_{12}) m_{123}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2}, \qquad (18)$$

$$M_{123} = \frac{c_{12}^2 m_{111}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{2c_{11}c_{12} m_{112}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} - \frac{2c_{12}(c_{11}+c_{12}) m_{122}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2} + \frac{\left(c_{11}^2 + 2c_{11}c_{12} + 2c_{12}^2\right) m_{123}}{(c_{11}-c_{12})^2 (c_{11}+2c_{12})^2}, \qquad (19)$$

$$M_{144} = \frac{m_{144}}{{c_{44}}^2}, \qquad (20)$$

$$M_{155} = \frac{m_{155}}{{c_{44}}^2}, \qquad (21)$$

$$M_{414} = \frac{(c_{11}+c_{12}) m_{414}}{(c_{11}-c_{12})(c_{11}+2c_{12}) c_{44}} - \frac{2c_{12} m_{424}}{\left({c_{11}}^2 + c_{11}c_{12} - 2{c_{12}}^2\right) c_{44}}, \qquad (22)$$

$$M_{424} = -\frac{c_{12} m_{414}}{\left(c_{11}{}^{2} + c_{11} c_{12} - 2 c_{12}{}^{2}\right) c_{44}} + \frac{c_{11} m_{424}}{\left(c_{11}{}^{2} + c_{11} c_{12} - 2 c_{12}{}^{2}\right) c_{44}}, \tag{23}$$

$$M_{456} = \frac{m_{456}}{c_{44}{}^{2}}, \tag{24}$$

$$\begin{aligned} R_{111} = {} & \frac{\left(c_{11}+c_{12}\right) m_{111} \left(c_{11} q_{11} + c_{12} \left(q_{11} - 2 q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{2 c_{12} m_{122} \left(c_{12} q_{11} - c_{11} q_{12}\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \\ & \frac{2 c_{12} m_{123} \left(c_{12} q_{11} - c_{11} q_{12}\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{2 m_{112} \left(c_{11}^{2} q_{12} + c_{11} c_{12} \left(-2 q_{11} + q_{12}\right) + 2 c_{12}^{2} \left(-q_{11} + q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \\ & \frac{\left(c_{11}+c_{12}\right) r_{111}}{\left(c_{11}-c_{12}\right)\left(c_{11}+2c_{12}\right)} - \frac{2 c_{12} r_{112}}{c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}}, \end{aligned} \tag{25}$$

$$\begin{aligned} R_{121} = {} & \frac{m_{122} \left(c_{11}^{2} q_{11} + 2 c_{12}^{2} q_{11} + c_{11} c_{12} \left(q_{11} - 4 q_{12}\right)\right)}{2 \left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{c_{11} m_{111} \left(-c_{12} q_{11} + c_{11} q_{12}\right)}{2 \left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \\ & \frac{m_{123} \left(-3 c_{11} c_{12} q_{11} - 2 c_{12}^{2} \left(q_{11} - 2 q_{12}\right) + c_{11}^{2} q_{12}\right)}{2 \left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{m_{112} \left(2 c_{12}^{2} q_{11} + c_{11}^{2} \left(q_{11} + 2 q_{12}\right) - c_{11} c_{12} \left(q_{11} + 4 q_{12}\right)\right)}{2 \left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} - \\ & \frac{c_{12} m_{414} q_{44}}{2 \left(c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}\right) c_{44}} + \frac{c_{11} m_{424} q_{44}}{2 c_{11}^{2} c_{44} + 2 c_{11} c_{12} c_{44} - 4 c_{12}^{2} c_{44}} + \frac{c_{11} r_{121}}{c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}} - \frac{c_{12} r_{123}}{c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}}, \end{aligned} \tag{26}$$

$$\begin{aligned} R_{112} = {} & \frac{m_{112} \left(c_{11}^{2} q_{11} + 2 c_{12}^{2} q_{11} + c_{11} c_{12} \left(q_{11} - 4 q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} - \frac{c_{12} m_{111} \left(c_{11} q_{11} + c_{12} \left(q_{11} - 2 q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \\ & \frac{c_{11} m_{122} \left(-c_{12} q_{11} + c_{11} q_{12}\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{c_{11} m_{123} \left(-c_{12} q_{11} + c_{11} q_{12}\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} - \frac{c_{12} r_{111}}{c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}} + \frac{c_{11} r_{112}}{c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}}, \end{aligned} \tag{27}$$

$$\begin{aligned} R_{123} = {} & \frac{m_{123} \left(c_{11}^{2} q_{11} + c_{11} c_{12} \left(2 q_{11} - 3 q_{12}\right) + 2 c_{12}^{2} \left(q_{11} - q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{c_{12} m_{111} \left(c_{12} q_{11} - c_{11} q_{12}\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \\ & \frac{m_{122} \left(c_{11}^{2} q_{12} + c_{11} c_{12} \left(-2 q_{11} + q_{12}\right) + 2 c_{12}^{2} \left(-q_{11} + q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \frac{m_{112} \left(c_{11}^{2} q_{12} + 2 c_{12}^{2} q_{12} - c_{11} c_{12} \left(2 q_{11} + q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)^{2} \left(c_{11}+2c_{12}\right)^{2}} + \\ & \frac{\left(c_{11}+c_{12}\right) m_{414} q_{44}}{2 \left(c_{11}-c_{12}\right)\left(c_{11}+2c_{12}\right) c_{44}} - \frac{c_{12} m_{424} q_{44}}{\left(c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}\right) c_{44}} - \frac{2 c_{12} r_{121}}{c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}} + \frac{\left(c_{11}+c_{12}\right) r_{123}}{\left(c_{11}-c_{12}\right)\left(c_{11}+2c_{12}\right)}, \end{aligned} \tag{28}$$

$$R_{144} = \frac{m_{414} \left(c_{11} q_{11} + c_{12} \left(q_{11} - 2 q_{12}\right)\right)}{2 \left(c_{11}^{2} + c_{11} c_{12} - 2 c_{12}^{2}\right) c_{44}} + \frac{-c_{12} m_{424} q_{11} + c_{11} m_{424} q_{12}}{\left(c_{11}-c_{12}\right)\left(c_{11}+2c_{12}\right) c_{44}} + \frac{m_{144} q_{44}}{2 c_{44}^{2}} + \frac{m_{456} q_{44}}{c_{44}^{2}} + \frac{r_{144}}{c_{44}}, \tag{29}$$

$$R_{155} = \frac{m_{414} (c_{11} q_{12} - c_{12} q_{11})}{\left(c_{11}-c_{12}\right)\left(c_{11}+2c_{12}\right) c_{44}} + \frac{m_{424} \left(-2 c_{12} q_{12} + c_{11} \left(q_{11} + q_{12}\right)\right)}{\left(c_{11}-c_{12}\right)\left(c_{11}+2c_{12}\right) c_{44}} + \frac{m_{155} q_{44}}{c_{44}^{2}} + \frac{r_{155}}{c_{44}} \tag{30}$$

As it was discussed in the main text of the paper, to obtain effective potential of a film, $\widetilde{G}$,

$$\widetilde{G} = G + \epsilon_1\sigma_1 + \epsilon_2\sigma_2 + \epsilon_6\sigma_6, \tag{31}$$

on applies mixed mechanical conditions

$$\begin{cases} \frac{\partial G}{\partial \sigma_1} = \epsilon_0, \frac{\partial G}{\partial \sigma_2} = \epsilon_0, \frac{\partial G}{\partial \sigma_6} = 0 \\ \sigma_3 = 0, \sigma_4 = 0, \sigma_5 = 0. \end{cases} \tag{32}$$

and eliminates σ_1, σ_2 and σ_6 between (31) and (32). High-order couplings described by tensors M_{ijk}, R_{ijk}, and N_{ijk} renormalize a_{ijk} coefficients of P^6-terms of G. The renormalization reads:

$$\begin{aligned} a^*_{111} = a_{111} &- \frac{M_{111}\left(Q_{11}s_{11} - Q_{12}s_{12}\right)^2}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \frac{M_{122}\left(Q_{12}^2 s_{11}^2 - 2Q_{11}Q_{12}s_{11}s_{12} + Q_{11}^2 s_{12}^2\right)}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\ &\frac{R_{112}\left(-Q_{12}s_{11}^3 + Q_{11}s_{11}^2 s_{12} + Q_{12}s_{11}s_{12}^2 - Q_{11}s_{12}^3\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \frac{R_{111}\left(-Q_{11}s_{11}^3 + Q_{12}s_{11}^2 s_{12} + Q_{11}s_{11}s_{12}^2 - Q_{12}s_{12}^3\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\ &\frac{M_{112}\left(-Q_{11}^2 s_{11}s_{12} - Q_{12}^2 s_{11}s_{12} + Q_{11}Q_{12}\left(s_{11}^2 + s_{12}^2\right)\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} + \\ &\frac{\left(Q_{11}+Q_{12}\right)}{3\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^3}({Q_{11}}^2\left({s_{11}}^2 N_{111} + s_{11}\left(N_{111} - 3N_{112}\right)s_{12} + N_{111}{s_{12}}^2\right) + \\ &{Q_{12}}^2\left({s_{11}}^2 N_{111} + s_{11}\left(N_{111} - 3N_{112}\right)s_{12} + N_{111}{s_{12}}^2\right) - \\ &Q_{11}Q_{12}\left({s_{11}}^2\left(N_{111} - 3N_{112}\right) + 4s_{11}N_{111}s_{12} + \left(N_{111} - 3N_{112}\right){s_{12}}^2\right)), \end{aligned} \tag{33}$$

$$a^*_{333} = a_{111} - \frac{M_{122}Q_{12}^2}{\left(s_{11}+s_{12}\right)^2} - \frac{M_{123}Q_{12}^2}{\left(s_{11}+s_{12}\right)^2} + \frac{2Q_{12}R_{112}}{s_{11}+s_{12}} + \frac{2{Q_{12}}^3\left(N_{111}+3N_{112}\right)}{3\left(s_{11}+s_{12}\right)^3}, \tag{34}$$

$$\begin{aligned} a^*_{112} = a_{112} &- \frac{M_{122}\left(Q_{11}^2 s_{11}\left(s_{11} - 2s_{12}\right) + Q_{12}^2 s_{12}\left(-2s_{11} + s_{12}\right) + 2Q_{11}Q_{12}\left(s_{11}^2 - s_{11}s_{12} + s_{12}^2\right)\right)}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\ &\frac{M_{112}\left(Q_{11}Q_{12}\left(s_{11}^2 - 4s_{11}s_{12} + s_{12}^2\right) + Q_{11}^2\left(s_{11}^2 - s_{11}s_{12} + s_{12}^2\right) + Q_{12}^2\left(s_{11}^2 - s_{11}s_{12} + s_{12}^2\right)\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\ &\frac{M_{155}Q_{44}^2\left(s_{11}^2 - s_{12}^2\right)^2}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2 s_{44}^2} - \frac{M_{424}\left(Q_{11}+Q_{12}\right)Q_{44}}{\left(s_{11}+s_{12}\right)s_{44}} + \frac{Q_{44}R_{155}\left(s_{11}^2 - s_{12}^2\right)^2}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2 s_{44}} - \\ &\frac{M_{111}\left(2Q_{11}Q_{12}s_{11}s_{44}^2(s_{11}-s_{12}) + Q_{12}^2 s_{11}^2 s_{44}^2 - 2Q_{11}^2 s_{11}s_{12}s_{44}^2 - 2Q_{11}Q_{12}s_{11}s_{12}s_{44}^2 - 2Q_{12}^2 s_{11}s_{12}s_{44}^2 + Q_{11}^2 s_{12}^2 s_{44}^2\right)}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2 s_{44}^2} - \\ &\frac{R_{111}\left(-Q_{12}s_{11}^3 s_{44}^2 + Q_{11}s_{11}^2 s_{12}s_{44}^2 + Q_{12}s_{11}s_{12}^2 s_{44}^2 - Q_{11}s_{12}^3 s_{44}^2\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2 s_{44}^2} - \\ &(R_{121}(-2Q_{11}s_{11}^3 s_{44}^2 - 2Q_{12}s_{11}^3 s_{44}^2 + 2Q_{11}s_{11}^2 s_{12}s_{44}^2 + 2Q_{12}s_{11}^2 s_{12}s_{44}^2 + 2Q_{11}s_{11}s_{12}^2 s_{44}^2 + 2Q_{12}s_{11}s_{12}^2 s_{44}^2 - \\ &2Q_{11}s_{12}^3 s_{44}^2 - 2Q_{12}s_{12}^3 s_{44}^2))/((s_{11}-s_{12})^2\left(s_{11}+s_{12}\right)^2 s_{44}^2) - \\ &\frac{R_{112}\left(-Q_{11}s_{11}^3 s_{44}^2 + Q_{12}s_{11}^2 s_{12}s_{44}^2 + Q_{11}s_{11}s_{12}^2 s_{44}^2 - Q_{12}s_{12}^3 s_{44}^2\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2 s_{44}^2} + \\ &\frac{\left(Q_{11}+Q_{12}\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^3 {s_{44}}^2}\left({Q_{44}}^2({s_{11}}^2 - {s_{12}}^2)^2 N_{155} + ({Q_{11}}^2({s_{11}}^2 N_{112} - s_{11}(N_{111}+N_{112})s_{12} + N_{112}{s_{12}}^2) + \right. \\ &{Q_{12}}^2({s_{11}}^2 N_{112} - s_{11}(N_{111}+N_{112})s_{12} + N_{112}{s_{12}}^2) + Q_{11}Q_{12}({s_{11}}^2(N_{111}+N_{112}) \text{- } 4s_{11}N_{112}s_{12} + (N_{111}+N_{112}){s_{12}}^2)){s_{44}}^2, \end{aligned} \tag{35}$$

$$
\begin{aligned}
a^*_{113} = a_{112} - \frac{M_{111}Q_{12}\left(Q_{11}s_{11}-Q_{12}s_{12}\right)}{\left(s_{11}-s_{12}\right)\left(s_{11}+s_{12}\right)^2} - \frac{M_{123}\left(Q_{11}Q_{12}s_{11}^2-Q_{11}^2s_{11}s_{12}-Q_{12}^2s_{11}s_{12}+Q_{11}Q_{12}s_{12}^2\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\
\frac{M_{112}\left(Q_{11}Q_{12}s_{11}^2+Q_{12}^2s_{11}^2-2Q_{11}Q_{12}s_{11}s_{12}-2Q_{12}^2s_{11}s_{12}+Q_{11}Q_{12}s_{12}^2+Q_{12}^2s_{12}^2\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\
\frac{R_{123}\left(-2Q_{12}s_{11}^3+2Q_{11}s_{11}^2s_{12}+2Q_{12}s_{11}s_{12}^2-2Q_{11}s_{12}^3\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\
\frac{R_{121}\left(-2Q_{11}s_{11}^3+2Q_{12}s_{11}^2s_{12}+2Q_{11}s_{11}s_{12}^2-2Q_{12}s_{12}^3\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\
\frac{R_{111}\left(-Q_{12}s_{11}^3+Q_{12}s_{11}^2s_{12}+Q_{12}s_{11}s_{12}^2-Q_{12}s_{12}^3\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \frac{R_{112}\left(-Q_{12}s_{11}^3+Q_{12}s_{11}^2s_{12}+Q_{12}s_{11}s_{12}^2-Q_{12}s_{12}^3\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\
\frac{M_{122}\left(2Q_{11}Q_{12}s_{12}\left(-3s_{11}+s_{12}\right)+Q_{11}^2\left(s_{11}^2+s_{12}^2\right)+Q_{12}^2\left(3s_{11}^2-2s_{11}s_{12}+s_{12}^2\right)\right)}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} + \\
\frac{Q_{12}}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^3}(4\,Q_{11}Q_{12}({s_{11}}^2N_{112}-s_{11}(N_{111}+N_{112})s_{12}+N_{112}{s_{12}}^2)+{Q_{11}}^2({s_{11}}^2(N_{111}+N_{112}) - \\
4s_{11}N_{112}s_{12}+(N_{111}+N_{112}){s_{12}}^2)+{Q_{12}}^2({s_{11}}^2(N_{111}+N_{112}-4s_{11}N_{112}s_{12}+(N_{111}+N_{112}){s_{12}}^2)),
\end{aligned}
\tag{36}
$$

$$
\begin{aligned}
a^*_{133} = a_{112} - \frac{M_{111}Q_{12}^2}{2\left(s_{11}+s_{12}\right)^2} - \frac{M_{112}Q_{12}^2}{\left(s_{11}+s_{12}\right)^2} - \frac{M_{123}Q_{12}\left(Q_{11}+Q_{12}\right)}{\left(s_{11}+s_{12}\right)^2} - \frac{M_{122}Q_{12}\left(2Q_{11}+3Q_{12}\right)}{2\left(s_{11}+s_{12}\right)^2} + \\
\frac{R_{112}\left(Q_{11}s_{11}+Q_{12}s_{11}+Q_{11}s_{12}+Q_{12}s_{12}\right)}{\left(s_{11}+s_{12}\right)^2} + \frac{R_{121}\left(2Q_{12}s_{11}+2Q_{12}s_{12}\right)}{\left(s_{11}+s_{12}\right)^2} + \frac{R_{123}\left(2Q_{12}s_{11}+2Q_{12}s_{12}\right)}{\left(s_{11}+s_{12}\right)^2} + \\
\frac{{Q_{12}}^2\left(Q_{11}+Q_{12}\right)\left(N_{111}+3N_{112}\right)}{\left(s_{11}+s_{12}\right)^3},
\end{aligned}
\tag{37}
$$

$$
\begin{aligned}
a^*_{123} = a_{123} - \frac{2M_{112}Q_{12}\left(Q_{11}+Q_{12}\right)}{\left(s_{11}+s_{12}\right)^2} + \frac{2M_{111}Q_{12}\left(-s_{11}+s_{12}\right)\left(Q_{12}s_{11}-Q_{11}s_{12}\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \\
\frac{M_{123}\left(-4Q_{11}Q_{12}s_{11}s_{12}+Q_{11}^2\left(s_{11}^2+s_{12}^2\right)+Q_{12}^2\left(s_{11}^2+s_{12}^2\right)\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} + \\
\frac{2M_{122}\left(Q_{11}^2s_{11}s_{12}+Q_{12}^2\left(2s_{11}-s_{12}\right)s_{12}-Q_{11}Q_{12}\left(2s_{11}^2-s_{11}s_{12}+s_{12}^2\right)\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2} - \frac{M_{144}Q_{44}^2\left(s_{11}^2-s_{12}^2\right)^2}{2\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2s_{44}^2} - \\
\frac{2M_{424}Q_{12}Q_{44}}{\left(s_{11}+s_{12}\right)s_{44}} + \frac{2Q_{44}R_{144}\left(s_{11}^2-s_{12}^2\right)^2}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2s_{44}} - \\
\frac{R_{123}\left(4Q_{11}s_{11}\left(s_{11}+s_{12}\right)\left(-s_{11}+s_{12}\right)s_{44}^2+4Q_{12}\left(-s_{11}-s_{12}\right)s_{12}\left(-s_{11}+s_{12}\right)s_{44}^2\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^2s_{44}^2} - \\
(R_{121}(8Q_{12}s_{11}\left(s_{11}+s_{12}\right)\left(-s_{11}+s_{12}\right)s_{44}^2+4Q_{11}\left(-s_{11}-s_{12}\right)s_{12}\left(-s_{11}+s_{12}\right)s_{44}^2 + \\
4Q_{12}\left(-s_{11}-s_{12}\right)s_{12}\left(-s_{11}+s_{12}\right)s_{44}^2))/((s_{11}-s_{12})^2\left(s_{11}+s_{12}\right)^2s_{44}^2) + \\
\frac{2Q_{12}N_{111}\left(2Q_{11}Q_{12}{s_{11}}^2{s_{44}}^2-2{Q_{11}}^2s_{11}s_{12}{s_{44}}^2-2{Q_{12}}^2s_{11}s_{12}{s_{44}}^2+2Q_{11}Q_{12}{s_{12}}^2{s_{44}}^2\right)}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^3{s_{44}}^2} + \\
\frac{2Q_{12}{Q_{44}}^2\left({s_{11}}^2-{s_{12}}^2\right)^2N_{155}}{\left(s_{11}-s_{12}\right)^2\left(s_{11}+s_{12}\right)^3{s_{44}}^2} + \\
(2Q_{12}N_{112}(2{Q_{11}}^2{s_{11}}^2{s_{44}}^2+2Q_{11}Q_{12}{s_{11}}^2{s_{44}}^2+2{Q_{12}}^2{s_{11}}^2{s_{44}}^2-2{Q_{11}}^2s_{11}s_{12}{s_{44}}^2 - \\
8Q_{11}Q_{12}s_{11}s_{12}{s_{44}}^2-2{Q_{12}}^2s_{11}s_{12}{s_{44}}^2+2{Q_{11}}^2{s_{12}}^2{s_{44}}^2+2Q_{11}Q_{12}{s_{12}}^2{s_{44}}^2+2{Q_{12}}^2{s_{12}}^2{s_{44}}^2))/ \\
((s_{11}-s_{12})^2\left(s_{11}+s_{12}\right)^3{s_{44}}^2)
\end{aligned}
\tag{38}
$$

Note that in (32) solutions were expanded in series and only low order terms of the expansion were kept, then σ_1, σ_2 and σ_6 were substituted into (31), therefore expressions (33 - 38) result from the expansion in series in (32).

Table III shows more detailed information for corrections $\Delta a^*_{111}, \Delta a^*_{112}$ and Δa^*_{123} demonstrating partial contributions from M_{ijk}, R_{ijk} and N_{ijk} tensors.

$M, [10^{-12}\frac{\mathrm{m}^4}{\mathrm{C}^2\mathrm{Pa}}]$ $R, [\frac{\mathrm{m}^8}{\mathrm{C}^4}]$	$\delta\ \Delta a^*_{111}$, $[10^9\frac{\mathrm{m}^9}{\mathrm{C}^4\mathrm{F}}]$
$a^{\mathrm{bulk}}_{111} = 8$	
M_{111} -5.6 ± 0.6	2.4
M_{112} 0.8 ± 0.5	-0.4
M_{122} 1.6 ± 0.6	-0.2
M_{123} < 0.5	0
M_{144} < 1.6	0
M_{155} 4.4 ± 1.4	0
M_{414} < 1	0
M_{424} < 1	0
M_{456} < 1	0
R_{111} 0.5 ± 0.1	14.7
R_{121} < 0.2	0
R_{112} 0.8 ± 0.1	-13.5
R_{123} -0.3 ± 0.2	0
R_{144} < 0.2	0
R_{155} < 0.2	0
N_{111} 8 ± 1	1.3
N_{112} < 2	0.1
N_{123} < 2	0
N_{144} < 2	0
N_{155} < 2	0
N_{456} < 4	0
Total	4.5

$M, [10^{-12}\frac{\mathrm{m}^4}{\mathrm{C}^2\mathrm{Pa}}]$ $R, [\frac{\mathrm{m}^8}{\mathrm{C}^4}]$	$\delta\ \Delta a^*_{112}$, $[10^9\frac{\mathrm{m}^9}{\mathrm{C}^4\mathrm{F}}]$
$a^{\mathrm{bulk}}_{112} = 5$	
M_{111} -5.6 ± 0.6	3.6
M_{112} 0.8 ± 0.5	-1.3
M_{122} 1.6 ± 0.6	-1.5
M_{123} < 0.5	0
M_{144} < 1.6	0
M_{155} 4.4 ± 1.4	-0.1
M_{414} < 1	0
M_{424} < 1	-0.2
M_{456} < 1	0
R_{111} 0.5 ± 0.1	8.4
R_{121} < 0.2	-18.5
R_{112} 0.8 ± 0.1	-23.6
R_{123} -0.3 ± 0.2	0
R_{144} < 0.2	0
R_{155} < 0.2	< 0.5
N_{111} 8 ± 1	0.3
N_{112} < 2	1.1
N_{123} < 2	0
N_{144} < 2	0
N_{155} < 2	< 0.1
N_{456} < 4	0
Total	-31.2

$M, [10^{-12}\frac{\mathrm{m}^4}{\mathrm{C}^2\mathrm{Pa}}]$ $R, [\frac{\mathrm{m}^8}{\mathrm{C}^4}]$	$\delta\ \Delta a^*_{123}$, $[10^9\frac{\mathrm{m}^9}{\mathrm{C}^4\mathrm{F}}]$
$a^{\mathrm{bulk}}_{123} = 5$	
M_{111} -5.6 ± 0.6	2.3
M_{112} 0.8 ± 0.5	-1.0
M_{122} 1.6 ± 0.6	-2.7
M_{123} < 0.5	1.2
M_{144} < 1.6	0
M_{155} 4.4 ± 1.4	0
M_{414} < 1	0
M_{424} < 1	-0.1
M_{456} < 1	0
R_{111} 0.5 ± 0.1	0
R_{121} < 0.2	-23.2
R_{112} 0.8 ± 0.1	0
R_{123} -0.3 ± 0.2	-35.3
R_{144} < 0.2	0.1
R_{155} < 0.2	0
N_{111} 8 ± 1	-0.3
N_{112} < 2	-1.1
N_{123} < 2	0
N_{144} < 2	0
N_{155} < 2	< 0.1
N_{456} < 4	0
Total	-61.6

TABLE III. Detailed information for corrections $\Delta a^*_{111}, \Delta a^*_{112}$ and Δa^*_{123}. δ means a contribution from a particular high-order electrostrictive coefficient. Values of a^{bulk}_{ijk} coefficients in $10^9\frac{\mathrm{m}^9}{\mathrm{C}^4\mathrm{F}}$ for bulk BaTiO_3 at 300K are also give for comparison.